



**Technical and Test Institute
for Construction Prague**

Prosecká 811/76a
190 00 Prague
Czech Republic
eota@tzus.cz



Member of



www.eota.eu

European Technical Assessment

**ETA 14/0325
of 25/10/2021**

Technical Assessment Body issuing the ETA: Technical and Test Institute
for Construction Prague

Trade name of the construction product

MOPURE for rebar connection

**Product family to which the construction
product belongs**

Product area code: 33
Post installed rebar connections
with MOPURE injection mortar
for a working life of 50 and/or 100 years

Manufacturer

Index Técnicas Expansivas, S.L.
P.I. La Portalada II C. Segador 13
26006 Logroño
Spain

Manufacturing plant

Index Plant 1

**This European Technical Assessment
contains**

17 pages including 13 Annexes which form
an integral part of this assessment.

**This European Technical Assessment is
issued in accordance with regulation
(EU) No 305/2011, on the basis of**

EAD 330087-01-0601

This version replaces

ETA 14/0325 issued on 22/08/2014

Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and should be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full (excepted the confidential Annex(es) referred to above). However, partial reproduction may be made, with the written consent of the issuing Technical Assessment Body - Technical and Test Institute for Construction Prague. Any partial reproduction has to be identified as such.

1. Technical description of the product

The MOPURE injection system is used for the connection, by anchoring or overlap joint, of reinforcing bars (rebars) in existing structures made of normal weight concrete. The design of the post-installed rebar connections is done in accordance with the regulations for reinforced concrete constructions.

Reinforcing bars made of steel with a diameter d from 8 to 32 mm and MOPURE chemical mortar are used for rebar connections. The steel element is placed into a drilled hole filled with injection mortar and is anchored via the bond between embedded element, injection mortar and concrete.

The illustration and the description of the product are given in Annex A.

2. Specification of the intended use in accordance with the applicable EAD

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The provisions made in this European Technical Assessment are based on an assumed working life of the anchor of 50 years and 100 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the products in relation to the expected economically reasonable working life of the works.

3. Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

| Essential characteristic | Performance |
|---------------------------------------------------|---------------|
| Bond strength of post-installed rebar | See Annex C 1 |
| Reduction factor | See Annex C 1 |
| Amplification factor for minimum anchorage length | See Annex C 1 |

3.2 Safety in case of fire (BWR 2)

| Essential characteristic | Performance |
|--------------------------|------------------------------------|
| Reaction to fire | Class (A1) according to EN 13501-1 |
| Resistance to fire | No performance assessed |

3.3 General aspects relating to fitness for use

Durability and serviceability are only ensured if the specifications of intended use according to Annex B 1 are kept.

4. Assessment and verification of constancy of performance (AVCP) system applied with reference to its legal base

According to the Decision 96/582/EC of the European Commission¹ the system of assessment verification of constancy of performance (see Annex V to Regulation (EU) No 305/2011) given in the following table apply.

| Product | Intended use | Level or class | System |
|-----------------------------------|------------------------------------------------------------------------------------------------------------------|----------------|--------|
| Metal anchors for use in concrete | For fixing and/or supporting concrete structural elements or heavy units such as cladding and suspended ceilings | - | 1 |

¹ Official Journal of the European Communities L 254 of 08.10.1996

5. Technical details necessary for the implementation of the AVCP system, as provided in the applicable EAD

The factory production control shall be in accordance with the control plan which is a part of the technical documentation of this European Technical Assessment. The control plan is laid down in the context of the factory production control system operated by the manufacturer and deposited at Technical and Test Institute for Construction Prague.² The results of factory production control shall be recorded and evaluated in accordance with the provisions of the control plan.

Issued in Prague on 25.10.2021

By

Ing. Mária Schaan

Head of the Technical Assessment Body



² The control plan is a confidential part of the documentation of the European Technical Assessment, but not published together with the ETA and only handed over to the approved body involved in the procedure of AVCP.

Mortar cartridges


Universal cartridge

MOPURE 250 ml




Side by side cartridge


MOPURE 400 ml

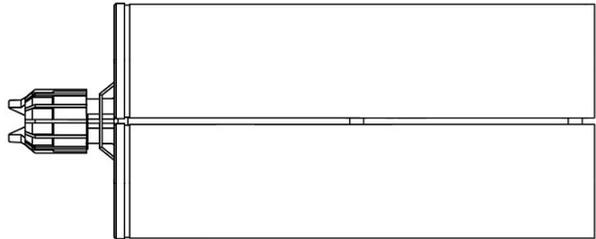

MOPURE 600 ml

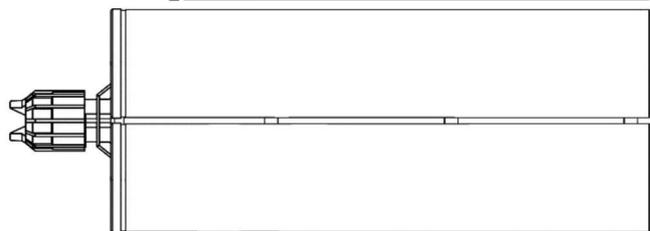


MOPURE 1500 ml

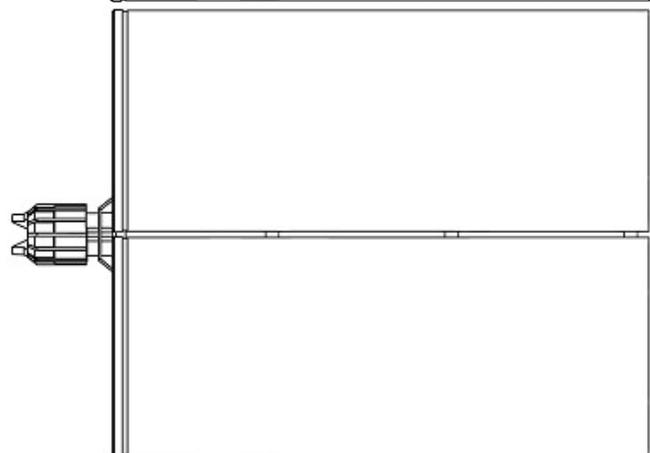


Mixing nozzle

Q mixing nozzle



QH mixing nozzle

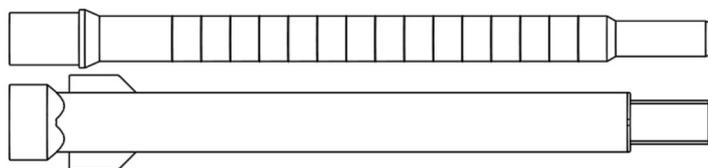

MOPURE for rebar connection

Product description
Injection system

Annex A 2

Rebar Ø8, Ø10, Ø12, Ø14, Ø16, Ø20, Ø25, Ø28, Ø32

Figure A6: Reinforcing bar



Minimum value of related rib area $f_{R,min}$ according to EN 1992-1-1:2004.

- The maximum outer rebar diameter over the ribs shall be:
Nominal diameter of the rib $d + 2 \cdot h$ ($h \leq 0,07 \cdot d$)
(d: nominal diameter of the bar; h: rib height of the bar)

Table A1: Materials

| Product form | | Bars and de-coiled rods | |
|------------------------------------------------------------|--------------------------------|-------------------------|-----------------------|
| Class | | B | C |
| Characteristic yield strength f_{yk} or $f_{0,2k}$ (MPa) | | 400 to 600 | |
| Minimum value of $k = (f_t / f_y)_k$ | | $\geq 1,08$ | $\geq 1,15$ < 1,35 |
| Characteristic strain at maximum force ϵ_{uk} (%) | | $\geq 5,0$ | $\geq 7,5$ |
| Bendability | | Bend / Rebend test | |
| Maximum deviation from nominal mass (individual bar) (%) | Nominal bar size (mm) ≤ 8 | $\pm 6,0$ | |
| | > 8 | $\pm 4,5$ | |
| Bond: Minimum relative rib area, $f_{R,min}$ | Nominal bar size (mm) 8 to 12 | 0,040 | |
| | > 12 | 0,056 | |

MOPURE for rebar connection

Product description
Rebar and materials

Annex A 3

Specifications of intended use

Anchorage subject to:

- Static and quasi-static load.

Base materials

- Reinforced or unreinforced normal weight concrete according to EN 206:2013
- Strength classes C12/15 to C50/60 according to EN 206:2013.
- Maximum chloride concrete of 0,40% (CL 0.40) related to the cement content according to EN 206:2013.
- Non-carbonated concrete.

Note: In case of a carbonated surface of the existing concrete structure the carbonated layer shall be removed in the area of the post installed rebar connection (with a diameter $d_s + 60$ mm) prior to the installation of the new rebar. The depth of concrete to be removed shall correspond to at least minimum concrete cover in accordance with EN 1992-1-1:2004.

The foregoing may be neglected if building components are new and not carbonated.

Temperature range:

- -40°C to $+80^{\circ}\text{C}$ (max. short. term temperature $+80^{\circ}\text{C}$ and max. long term temperature $+40^{\circ}\text{C}$)

Use conditions (Environmental conditions)

- The rebars may be used in dry or wet concrete.

Design:

- The anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the forces to be transmitted.
- Design according to EN 1992-1-1 and EN 1992-1-2.
- The position of the reinforcement in the existing structure shall be determined on the basis of the construction documentation and taken into account when designing.

Installation:

- Dry or wet concrete.
- It must not be installed in flooded holes.
- Hole drilling by hammer drill or compressed air drill mode.
- The installation of post-installed rebars shall be done only by suitable trained installer and under supervision on site. The conditions under which an installer may be considered as suitable trained and the conditions for supervision on site are up to the Member States in which the installation is done.
- Check the position of the existing rebars (if the position is not known, it shall be determined using a rebar detector suitable for this purpose).


MOPURE for rebar connection

Intended use
Specifications

Annex B 1

Figure B1: General design rules of construction for bonded-in rebars

- Only tension forces in the axis of the rebar may be transmitted
- The transfer of shear forces between new concrete and existing structure shall be designed additionally according to EN 1992-1-1.
- The joints for concreting must be roughened to at least such an extent that aggregate protrude.

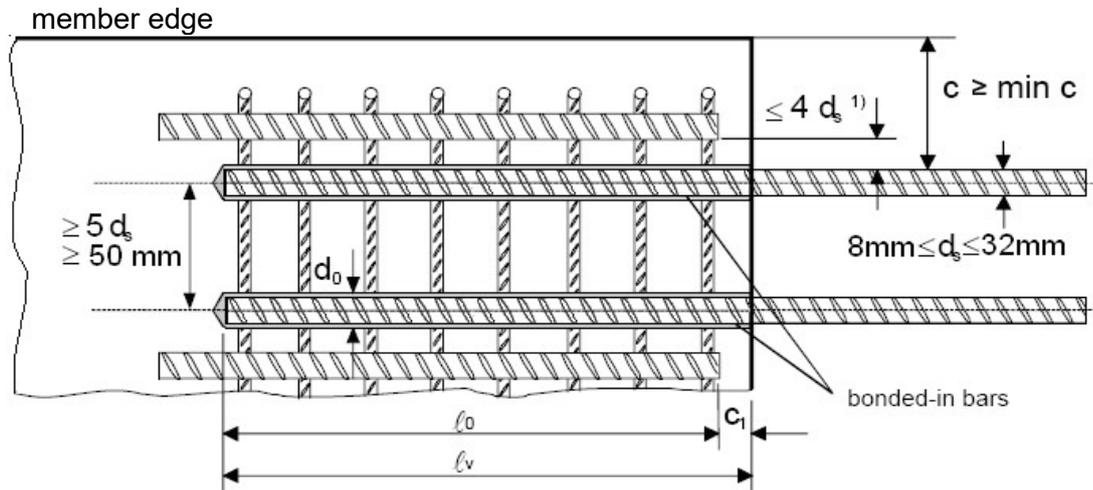

1) If the clear distance between lapped bars exceeds $4d_s$ then the lap length shall be increased by the difference between the clear bar distance and $4d_s$

- c concrete cover of bonded-in bar
- c_1 concrete cover at end-face of bonded-in bar
- min c minimum concrete cover acc. Table B1 of this assessment
- d_s diameter of bonded-in bar
- l_0 lap length acc. to EN 1992-1-1:2004
- l_v effective embedment depth $\geq l_0 + c_1$
- d_0 nominal drill bit diameter, see Table B2

MOPURE for rebar connection


Intended use
General design rules of construction

Annex B 2

Table B1: Minimum concrete cover c_{min} depending on drilling method

| Drilling method | Bar diameter ϕ | Without drilling aid | With drilling aid |
|-------------------------|---------------------|--------------------------------|--------------------------------|
| | | c_{min} | c_{min} |
| Hammer drilling | < 25 mm | 30 mm + 0,06 $l_v \geq 2 \phi$ | 30 mm + 0,02 $l_v \geq 2 \phi$ |
| | ≥ 25 mm | 40 mm + 0,06 $l_v \geq 2 \phi$ | 40 mm + 0,02 $l_v \geq 2 \phi$ |
| Compressed air drilling | < 25 mm | 50 mm + 0,08 l_v | 50 mm + 0,02 l_v |
| | ≥ 25 mm | 60 mm + 0,08 $l_v \geq 2 \phi$ | 60 mm + 0,02 $l_v \geq 2 \phi$ |

Figure B2: Example of drilling aid

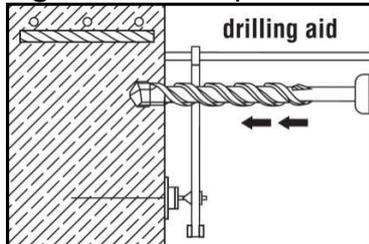

Minimum anchorage length $l_{bd,PIR}$ and minimum anchorage lap length $l_{0,PIR}$

Minimum anchorage length

$$l_{bd,PIR} = \alpha_{ib} \cdot l_{b,min}$$

$\alpha_{ib} = \alpha_{ib,100y}$ = amplification factor for minimum anchorage length
(see Annex C 1, Table C2 for hammer drilling method)

$l_{b,min}$ = minimum anchorage length of cast-in rebar according to EN 1992-1-1, eq. 8.6

Minimum lap length

$$l_{0,PIR} = \alpha_{ib} \cdot l_{0,min}$$

$\alpha_{ib} = \alpha_{ib,100y}$ = amplification factor for minimum anchorage length
(see Annex C 1, Table C2 for hammer drilling method)

$l_{0,min}$ = minimum lap length of cast-in rebar according to EN 1992-1-1, eq. 8.11

Table B2: Drilling diameter and maximum anchorage depth

| Rebar diameter $d_{nom}^{1)}$ [mm] | Nominal drilling diameter d_{cut} [mm] | Max permissible embedment depth l_v [mm] |
|------------------------------------------|------------------------------------------------|--------------------------------------------------|
| 8 | 12 | 400 |
| 10 | 14 | 500 |
| 12 | 16 | 600 |
| 14 | 18 | 700 |
| 16 | 20 | 800 |
| 20 | 25 | 1000 |
| 25 | 32 | 1000 |
| 28 | 35 | 1000 |
| 32 | 40 | 1000 |

¹⁾ The maximum outer rebar diameter over the ribs shall be:
nominal diameter of the bar $d_{nom} + 0,20 d_{nom}$

MOPURE for rebar connection

Intended use

Minimum concrete cover
Minimum anchorage length
Maximum embedment length

Annex B 3

Table B3: Processing and Cure time

| Concrete temperature [°C] | Gel time [minutes] | Cure time [hours] |
|-------------------------------------------------------|-------------------------------|------------------------------|
| +5 to +10 | 20 | 24 |
| +10 to +15 | | 12 |
| +15 to +20 | 15 | 8 |
| +20 to +25 | 11 | 7 |
| +25 to +30 | 8 | 6 |
| +30 to +35 | 6 | 5 |
| +35 to +40 | 4 | 4 |
| +40 | 3 | 3 |
| Cartridge must be conditioned to minimum +10°C | | |

MOPURE for rebar connection

Intended use
Processing and Load time

Annex B 4

Table B4: Applicator gun

A



B



C



D



E



| Cartridge | Applicator gun |
|-------------------|----------------|
| Universal 250 | A |
| Side by Side 400 | B |
| Side by Side 600 | C, D |
| Side by Side 1500 | E |

MOPURE for rebar connection

Intended use
Applicator gun

Annex B 5

Table B5: Brush

| Sizes | Ø8 | Ø10 | Ø12 | Ø14 | Ø16 | Ø20 | Ø25 | Ø28 | Ø32 |
|--------------------------------|----------|----------|-----|-----|-----|-----|-----|-----|-----|
| Drill hole diameter d_0 [mm] | 12 | 14 | 16 | 18 | 20 | 25 | 32 | 35 | 40 |
| Steel brush diameter [mm] | 12 13 | 14 15 | 18 | 22 | | 27 | 35 | 38 | 43 |
| Brushes head length [mm] | 75 | | | | | | | | |

If required use additional accessories and extension for air nozzle and brush to reach back of hole.

| Max. hole depth | Brush / extension configuration | Part |
|-----------------|----------------------------------------------------|-----------------|
| 375 mm | Brush head unit + handle unit | (a)+(b) |
| 675 mm | Brush head unit + extension piece + handle unit | (a)+(c)+(b) |
| 975 mm | Brush head unit + 2x extension piece + handle unit | (a)+(c)+(c)+(b) |

Part (a)



Part (b)



Part (c)

**Table B6: Extension hose for deep holes**

| Sizes | Ø8 | Ø10 | Ø12 | Ø14 | Ø16 | Ø20 | Ø24 | Ø25 | Ø26 | Ø28 | Ø32 |
|---------------------|----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|
| Hole diameter [mm] | 12 | 14 | 16 | 18 | 20 | 25 | 32 | 32 | 32 | 35 | 40 |
| Extension hose [mm] | 9 | | 14 | | | | | | | | |
| Resin stopper [mm] | - | - | - | - | 18 | 22 | 30 | | | 36 | |


MOPURE for rebar connection**Intended use**

Brush

Extension hose for deep holes

Annex B 6


Drilling the hole



Drill hole to the required embedment depth using a hammer-drill with carbide drill bit set in rotation hammer mode, or a compressed air drill or diamond core drill.




Rotary hammer drilling

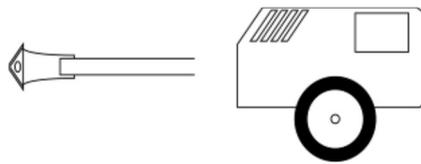

Compressed air drill

Before drilling remove carbonized concrete.


In case of aborted drill hole the drill hole shall be filled with mortar.

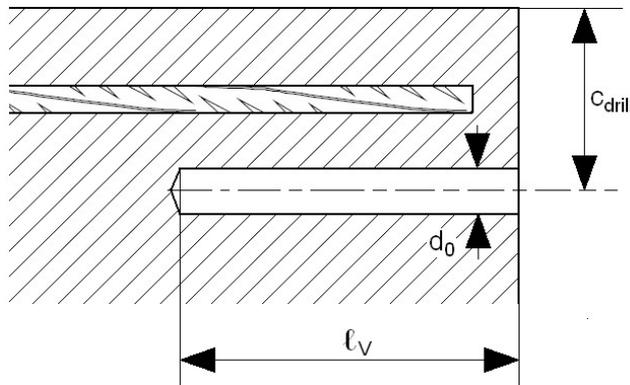

- Observe concrete coverage c , as per setting plan and Table B1
- Drill parallel to the edge and to existing rebar

Cleaning the hole

The borehole must be free of dust, debris, water, ice, oil, grease and other contaminants prior to mortar injection.

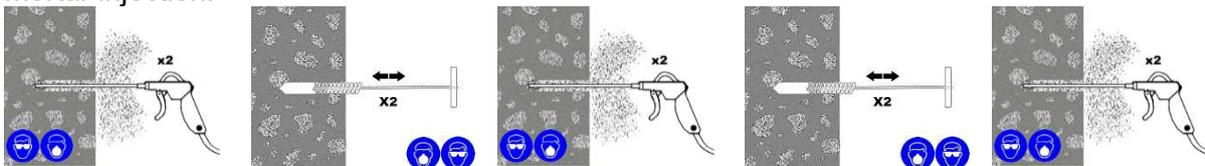

- Blowing 2 time from the back of the hole with oil-free compressed air (min. 6 bar) until return air stream is free of noticed dust.
- Brushing 2 time with the special brush size (brush $\varnothing \geq$ borehole \varnothing) by inserting the brush to the back of the hole in a twisting motion. The brush shall produce natural resistance as it enters the anchor hole. If this is not the case, please use a new brush or a brush with a larger diameter.
- Repeat operation 1 and 2.
- Blowing 1 time again with compressed air until return air stream is free of noticeable dust.


MOPURE for rebar connection

Intended use
Installation instructions I

Annex B 7

Mortar injection

If the hole collects water after initial cleaning, this water must be removed before injecting the resin.

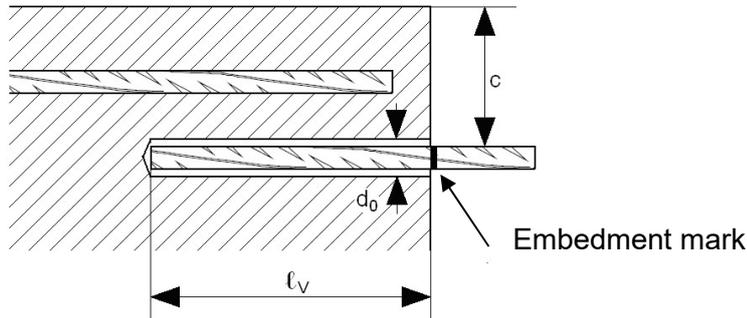


Before use, make sure the rebar is dry and free of oil or other residue.

Mark embedment depth on the rebar (e.g. with tape) l_v

Insert rebar in borehole, to verify hole and setting depth l_v


- Check expiration date: See imprint on cartridge. Do not use an expired product
- Cartridge temperature:
Must be between +10°C and +40°C when in use
- Base material temperature at time of installation:
Must be between +5°C and +40°C
- Instructions for transport and storage:
Keep in a cool, dry and dark place at +5°C to +20°C achieve maximum shelf life

Select the appropriate static mixer nozzle for the installation, open the cartridge/foil and screw onto the mouth of the cartridge. Insert the cartridge into the correct applicator gun.

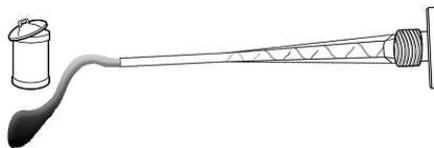

Extrude the first part of the cartridge to waste until an even colour has been achieved without streaking in the resin

If necessary, cut the extension tube to the depth of the hole and push onto the end of the mixer nozzle, and (for rebars 16 mm dia. or more) fit the correct resin stopper to the other end. Attach extension tubing and resin stopper.

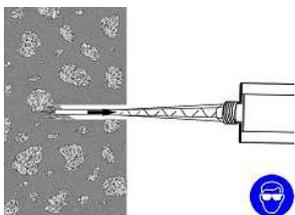


Insert the mixer nozzle (resin stopper / extension tube if applicable) to the bottom of the hole. Begin to extrude the resin and slowly withdraw the mixer nozzle from the hole ensuring that there are no air voids as the mixer nozzle is withdrawn. Fill the hole to approximately $\frac{1}{2}$ to $\frac{3}{4}$ full and remove the mixer nozzle completely.

MOPURE for rebar connection

Intended use
Installation instructions II

Annex B 8

Inserting the rebar

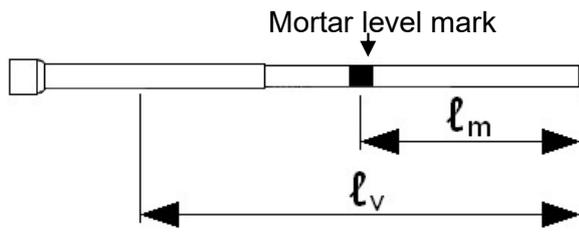


Mark the required mortar level l_m and embedment depth l_v with tape or marker on the injection extension.

Quick estimation: $l_m = 1/2 \cdot l_v$


Continue injection until the mortar level mark l_m becomes visible.



Insert the rebar, free from oil or other release agents, to the bottom of the hole using a back and forth twisting motion ensuring all the threads are thoroughly coated. Adjust to the correct position within the stated working time.

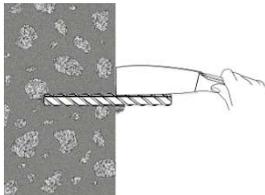

Any excess resin should be expelled from the hole evenly around the steel element showing that the hole is full. This excess resin should be removed from around the mouth of the hole before it sets.



Leave the anchor to cure.

Do not disturb the anchor until the appropriate loading/curing time has elapsed depending on the substrate conditions and ambient temperature.

MOPURE for rebar connection

Intended use
Installation instructions III

Annex B 9

Design bond strength of post-installed rebar $f_{bd,PIR}$ and $f_{bd,PIR,100y}$ for working life 50 and 100 years

$$f_{bd,PIR} = k_b \cdot f_{bd}$$

k_b = reduction factor

f_{bd} = design bond strength of cast-in rebar according to EN 1992-1-1

Table C1: Values of the design bond strength of post installed rebar $f_{bd,PIR} = f_{bd,PIR,100y}$ with reduction factor $k_b = k_{b,100y}$ for all drilling methods for good bond conditions

| Rebar Ø 8 to Ø 14 | | | | | | | | | |
|-----------------------------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
| Concrete class | C12/15 | C16/20 | C20/25 | C25/30 | C30/37 | C35/45 | C40/50 | C45/55 | C50/60 |
| k_b [-] | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 0,92 | 0,86 |
| $f_{bd,PIR}$ [N/mm ²] | 1,6 | 2,0 | 2,3 | 2,7 | 3,0 | 3,4 | 3,7 | | |
| Rebar Ø 16 | | | | | | | | | |
| Concrete class | C12/15 | C16/20 | C20/25 | C25/30 | C30/37 | C35/45 | C40/50 | C45/55 | C50/60 |
| k_b [-] | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 0,92 | 0,93 |
| $f_{bd,PIR}$ [N/mm ²] | 1,6 | 2,0 | 2,3 | 2,7 | 3,0 | 3,4 | 3,7 | | 4,0 |
| Rebar Ø 20 to Ø 26 | | | | | | | | | |
| Concrete class | C12/15 | C16/20 | C20/25 | C25/30 | C30/37 | C35/45 | C40/50 | C45/55 | C50/60 |
| k_b [-] | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 0,93 |
| $f_{bd,PIR}$ [N/mm ²] | 1,6 | 2,0 | 2,3 | 2,7 | 3,0 | 3,4 | 3,7 | 4,0 | |
| Rebar Ø 28 | | | | | | | | | |
| Concrete class | C12/15 | C16/20 | C20/25 | C25/30 | C30/37 | C35/45 | C40/50 | C45/55 | C50/60 |
| k_b [-] | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 1,0 | 0,92 | 0,86 |
| $f_{bd,PIR}$ [N/mm ²] | 1,6 | 2,0 | 2,3 | 2,7 | 3,0 | 3,4 | 3,7 | | |
| Rebar Ø 32 | | | | | | | | | |
| Concrete class | C12/15 | C16/20 | C20/25 | C25/30 | C30/37 | C35/45 | C40/50 | C45/55 | C50/60 |
| k_b [-] | 1,0 | 1,0 | 1,0 | 1,0 | 0,88 | 0,90 | 0,82 | 0,76 | 0,71 |
| $f_{bd,PIR}$ [N/mm ²] | 1,6 | 2,0 | 2,3 | 2,7 | | 3,0 | | | |

Tabulated values are valid for good bond conditions according to EN 1992-1-1.
For all other bond conditions multiply the values by 0,7.

Table C2: Amplification factor for minimum anchorage length for all drilling methods

| Rebar | Amplification factor | Concrete class C12/15 to C50/60 |
|-------------|----------------------------------|------------------------------------|
| Ø 8 to Ø 32 | $\alpha_{lb} = \alpha_{lb,100y}$ | 1,5 |

MOPURE for rebar connection

Performances

Design values of the ultimate bond resistance for hammer drilling

Annex C 1